

Low Temperature Atomic Layer Deposition of Tin Dioxide, SnO₂

Jaeyeong Heo, Adam S. Hock and Roy G. Gordon

*Harvard University
Cambridge, MA USA*

Outline

Earth-abundant, non-toxic transparent conductor: SnO₂

ALD process for SnO₂
new tin precursor
growth per cycle

SnO₂ film properties
composition
structure
optical properties
electrical properties
applications

SnO₂: Transparent Conductor and Heat Mirror

High visible transmission (high bandgap ($E_g \sim 4.1$ eV))

High electrical conductivity (high electron concentration and mobility)

High environmental stability

Constituent elements are non-toxic and abundant

**Known ALD processes require high temperatures, > 200 °C
or produce impure films (C, N), amorphous, low conductivity**

Tin(II) Cyclic Stannylylene as ALD Precursor



***N*²,*N*³-di-*tert*-butyl-butane-2,3-diamido-tin(II)**

Hydrocarbon ligand => high volatility (30 Torr at 60 °C)

Chelate structure => thermal stability

Sn-N bonds => reactive to hydrogen peroxide, H₂O₂

Synthesis and properties described by Adam Hock, Wednesday 14:15


ALD Process for SnO₂

Source temperature: 40 °C



Substrate temperature: 120 °C

Growth per cycle: 0.18 nm

Induction period: only a few cycles

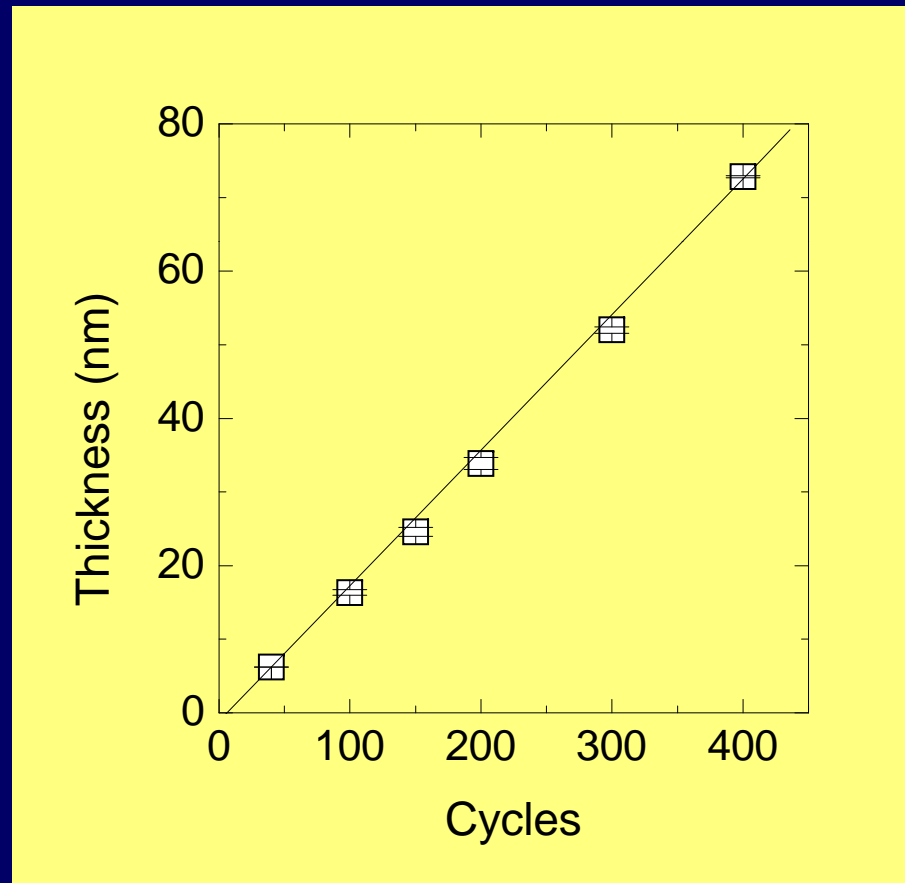

ALD Saturation Curves

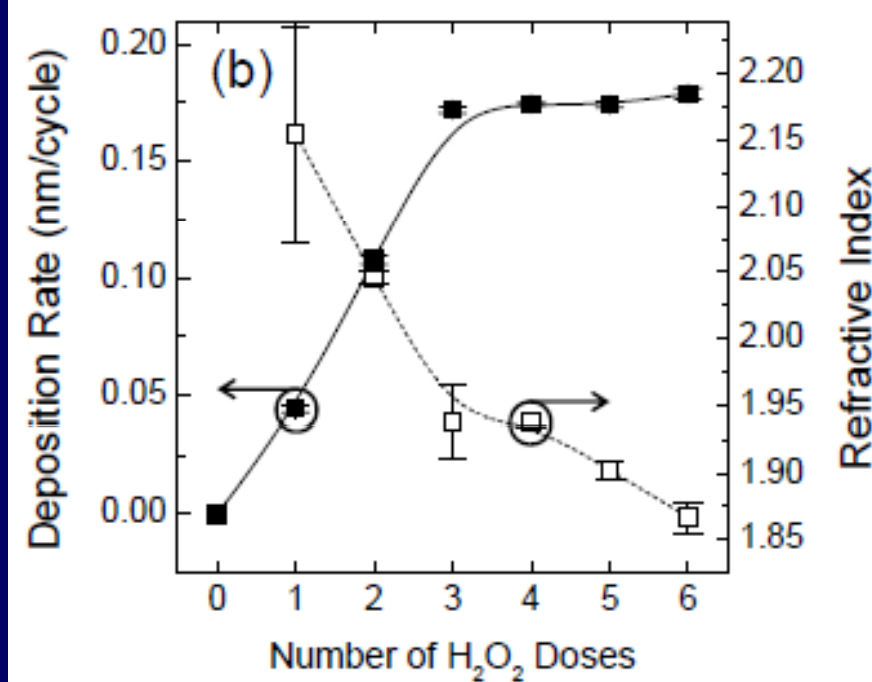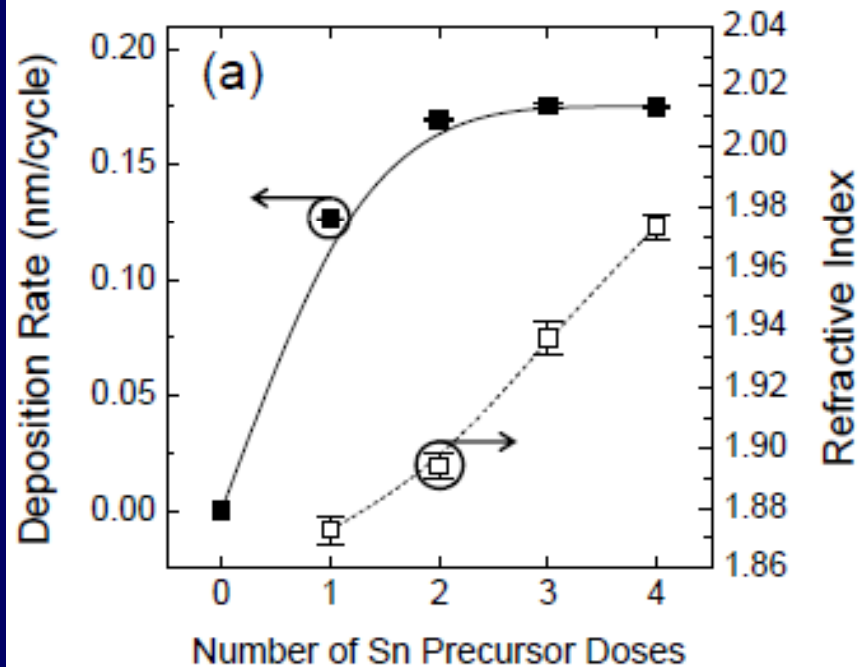


Increasing doses of cyclic stannylene precursor for tin

Increasing doses of oxygen precursor, hydrogen peroxide

Refractive index ~ 1.94 for saturated growth (3 doses)


Temperature Dependence of Growth

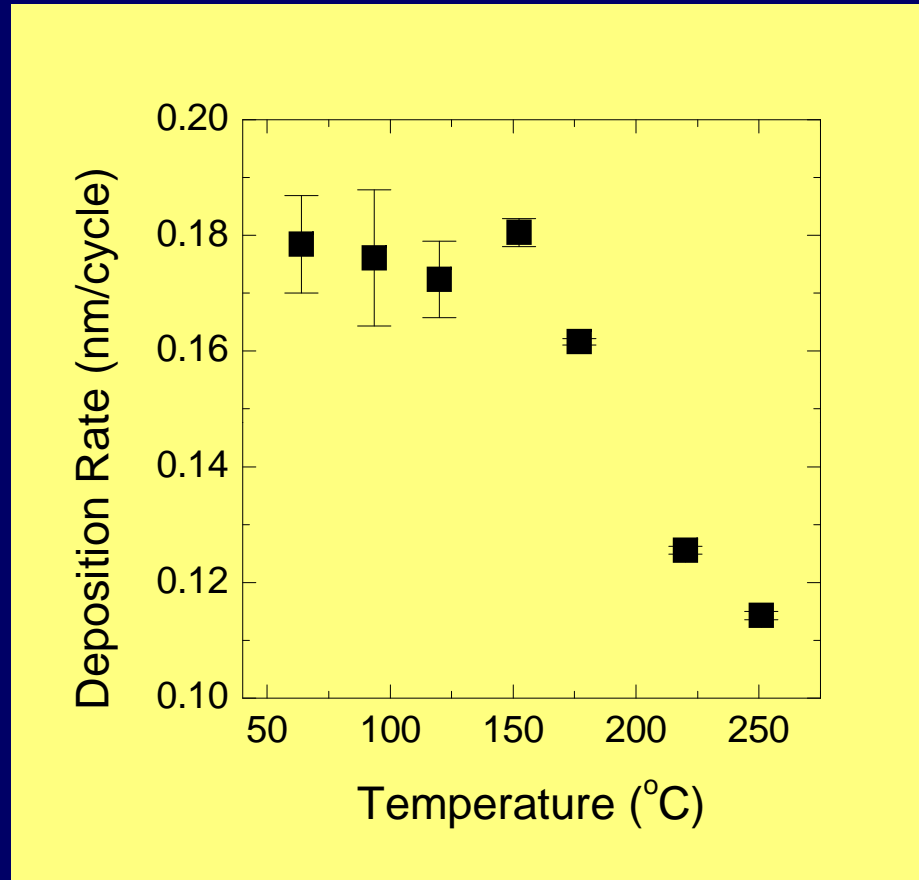


ALD window from 50 to 150 °C

SnO_x Composition

Rutherford Backscattering Spectroscopy (RBS)

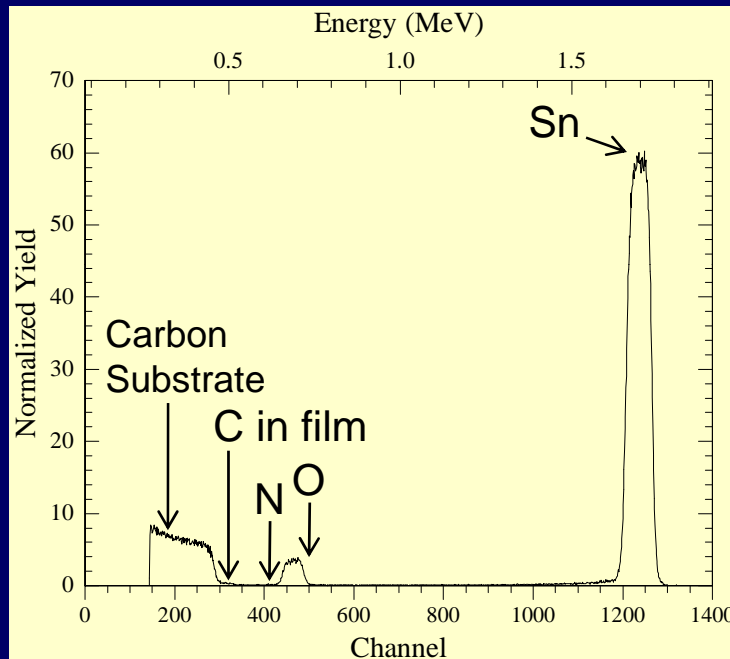


No C or N in film

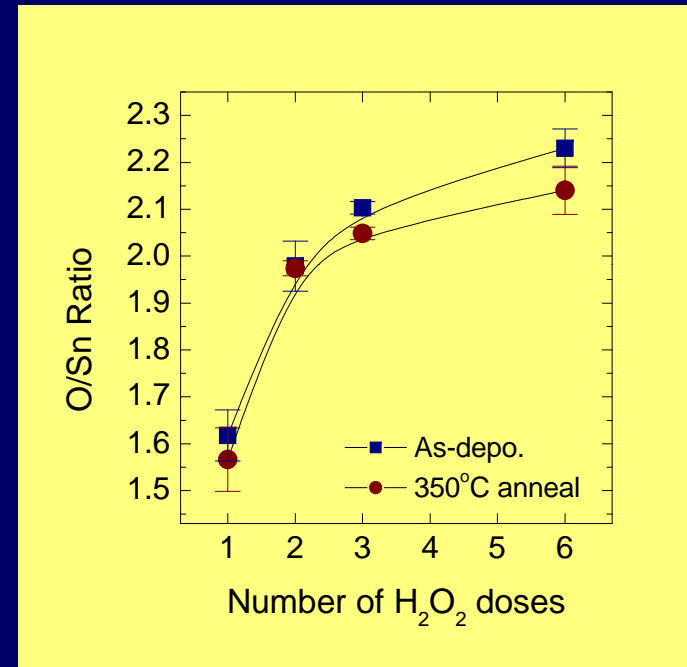




SnO₂ for 2-3 doses

X-Ray Photo-Electron Spectroscopy (XPS)

No impurities detected (C, N) inside film

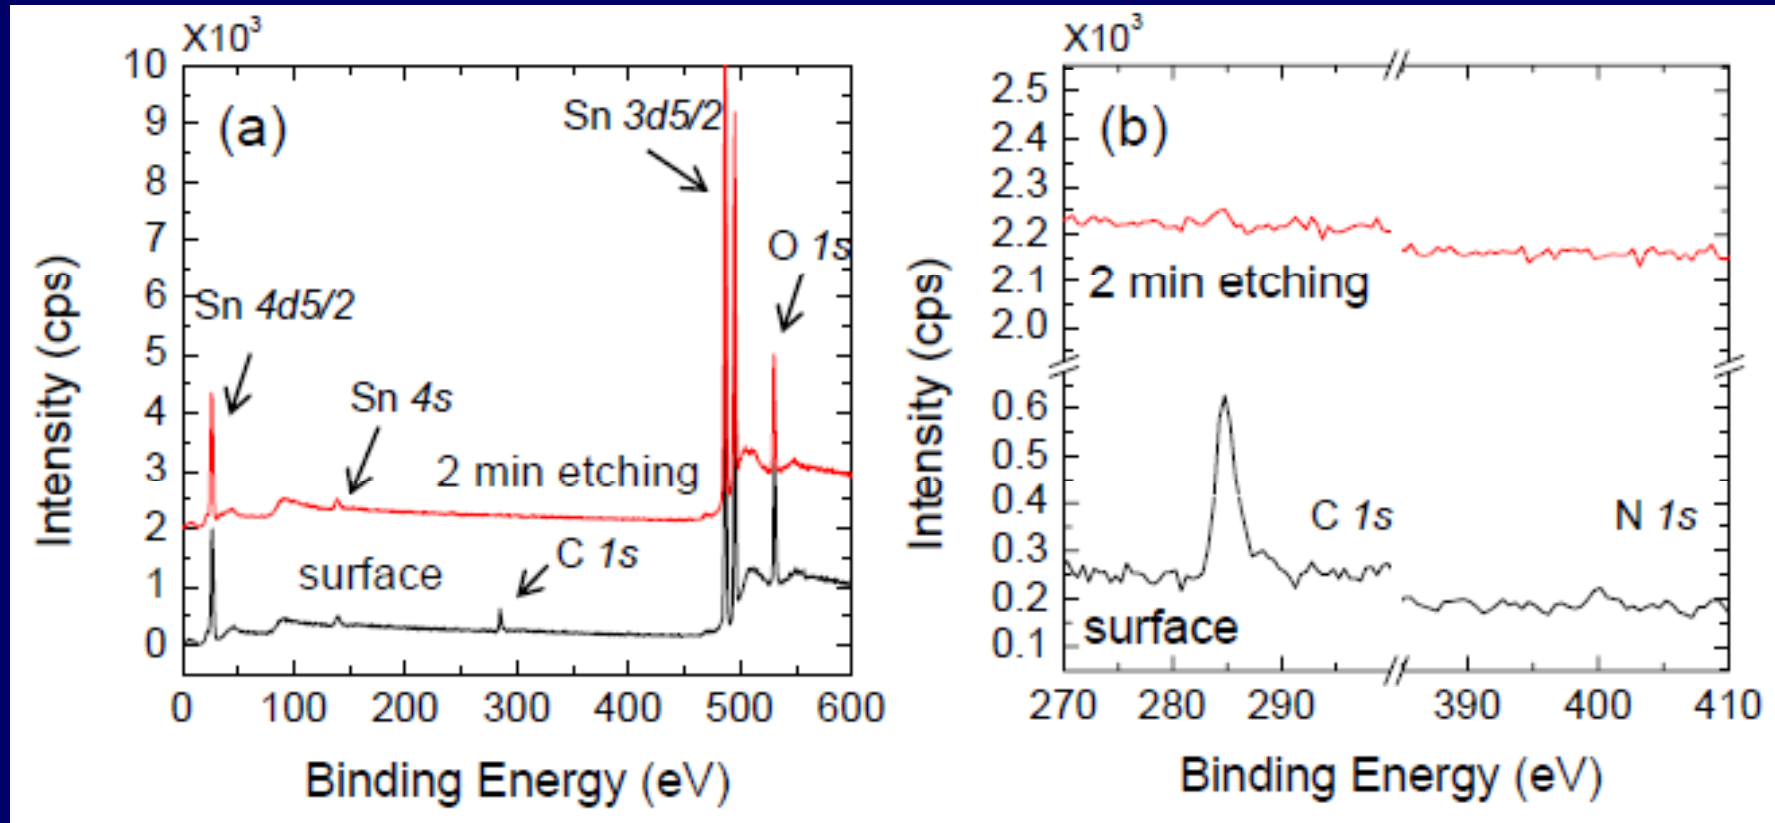

Smooth Morphology of SnO₂ Films

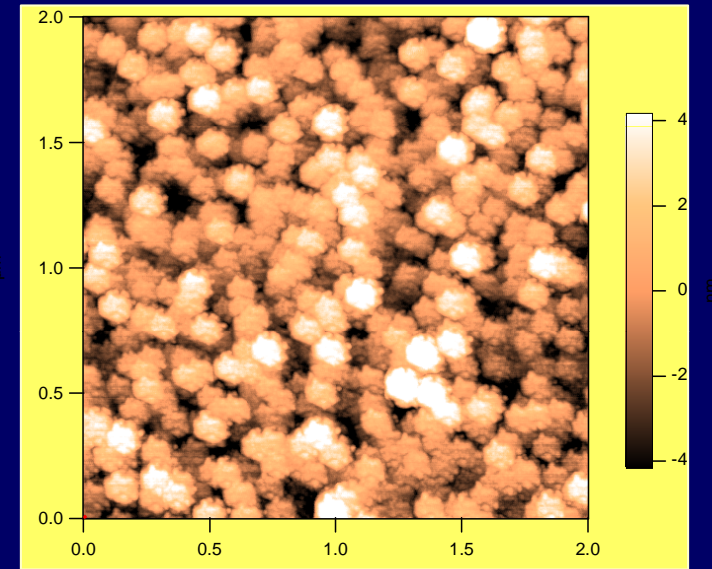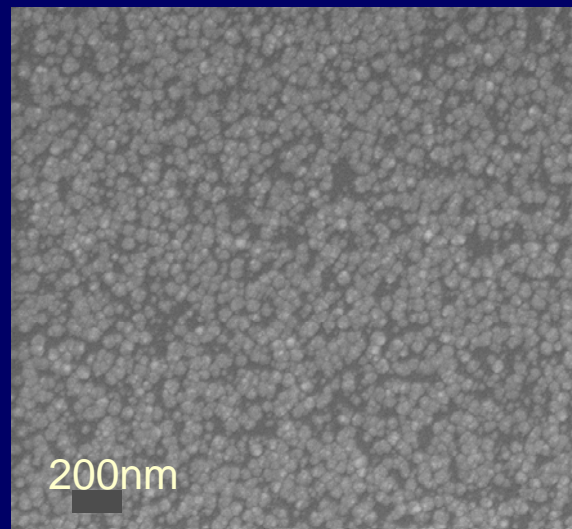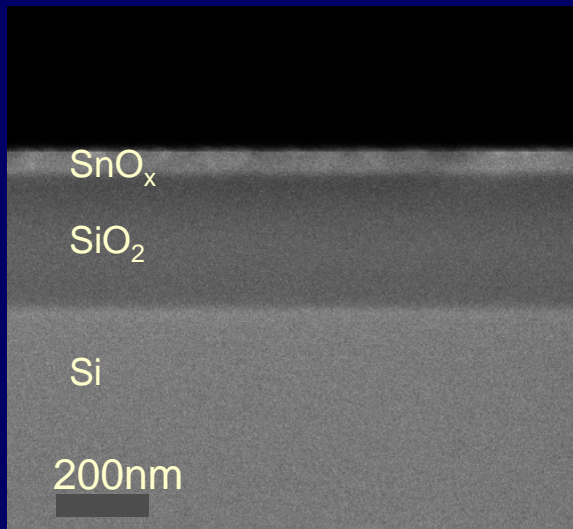


400 cycles => 71 nm

AFM
RMS roughness = 2 nm
< 3 % of thickness



Step Coverage

Uniform thickness in holes
with aspect ratio 50:1,
grown at 50 °C


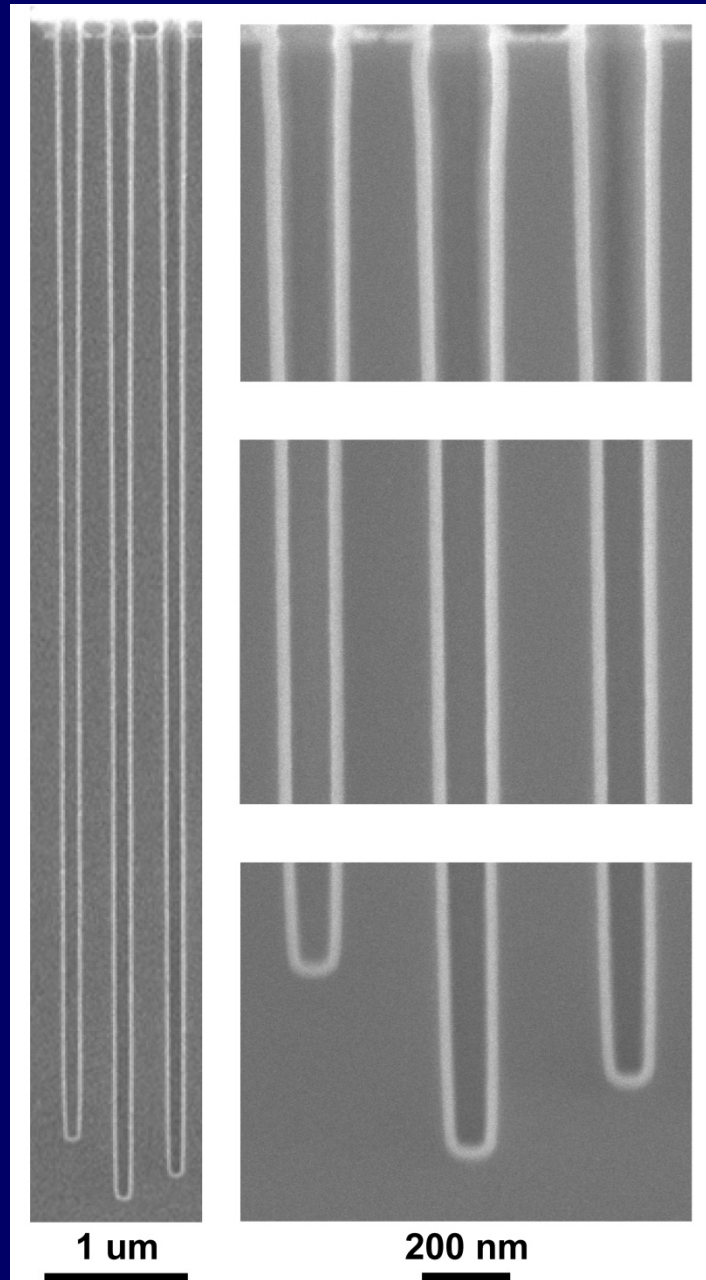


Polycrystalline Rutile Structure of SnO₂ Films


TEM

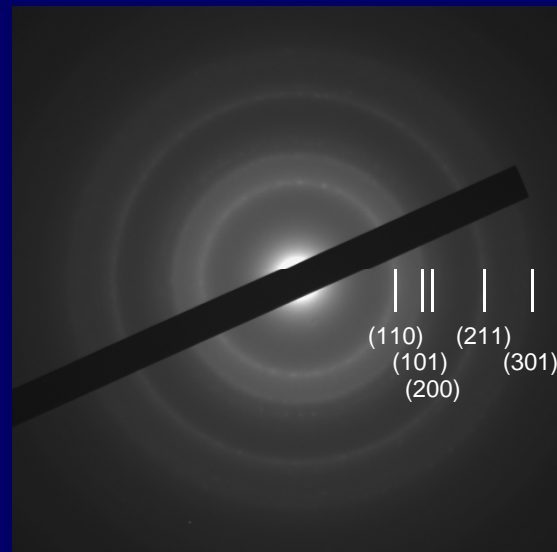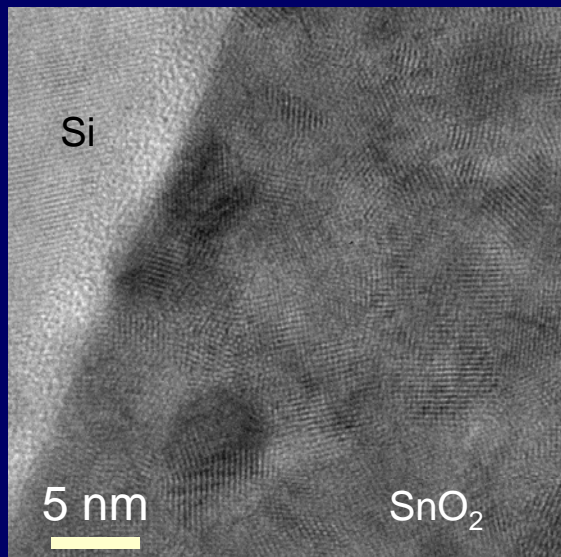

electron
diffraction

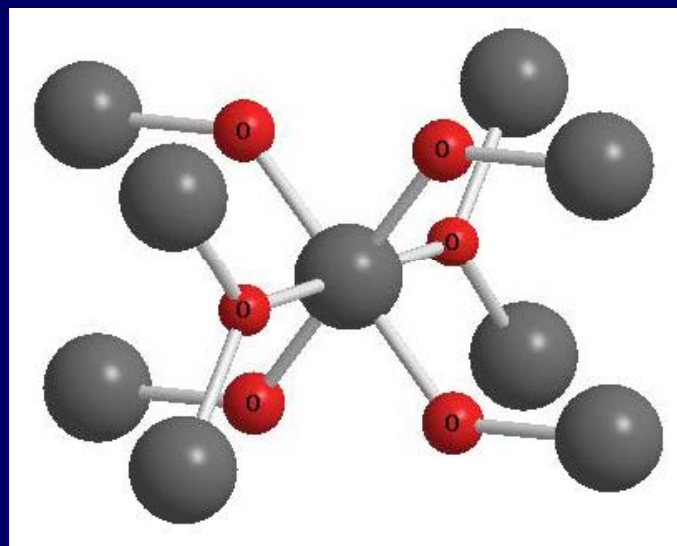
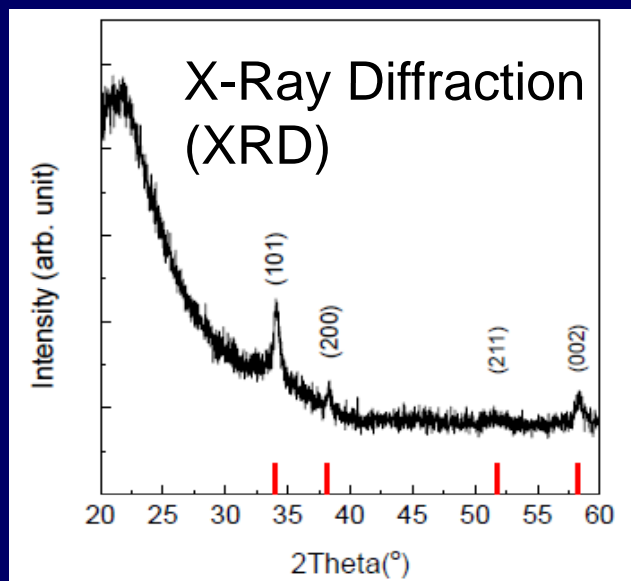


SnO₂ has Very Little Visible Absorption

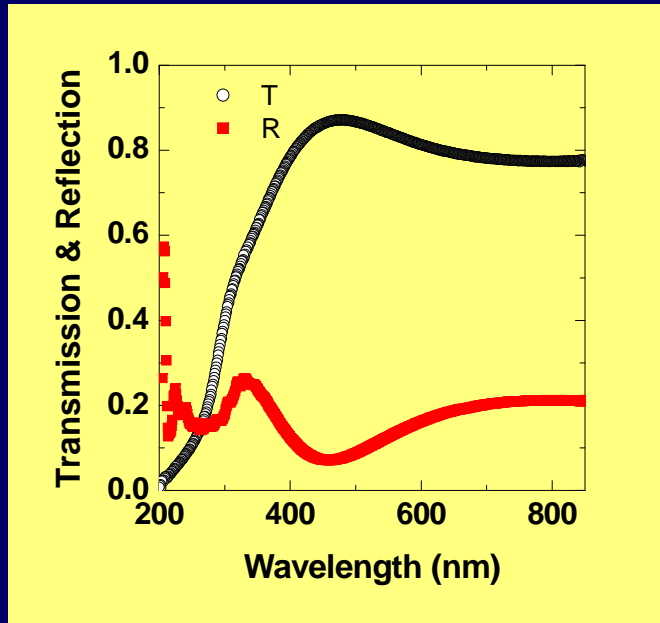


film 100 nm thick

Band gap 4.13 eV

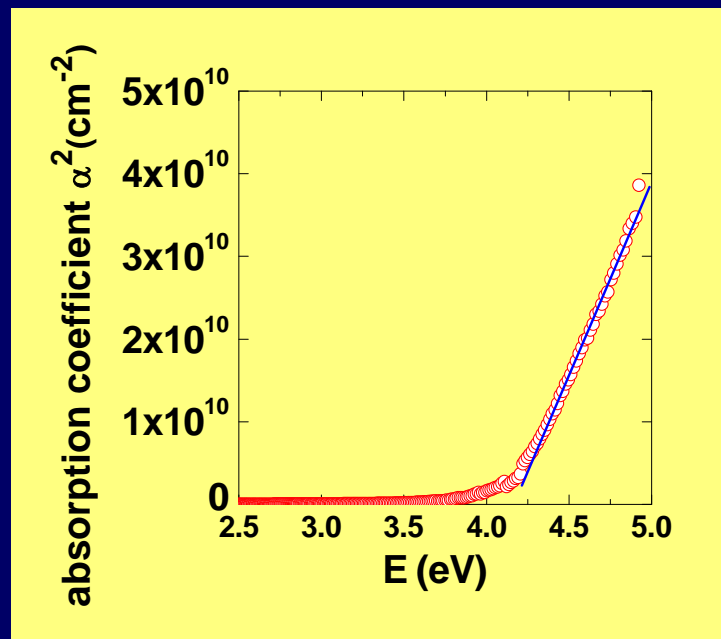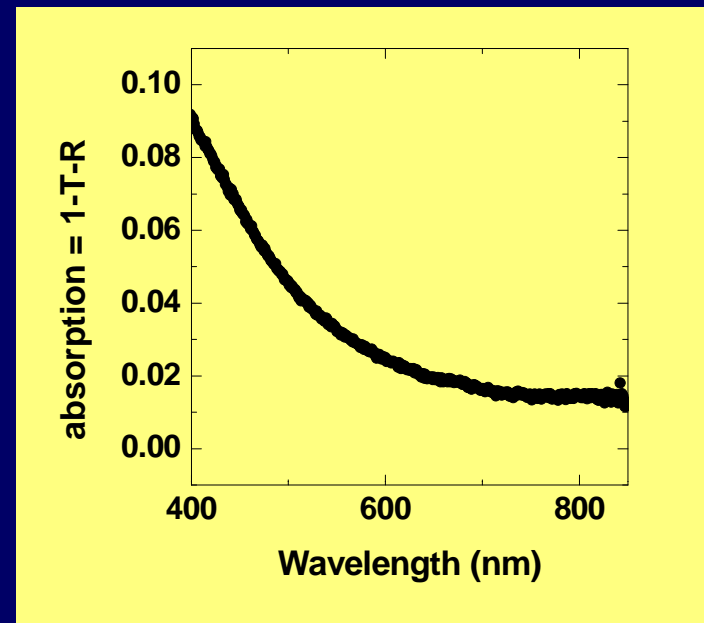

Electrical Properties

Resistivity minimum for stoichiometric SnO_2 (2 to 4 doses)

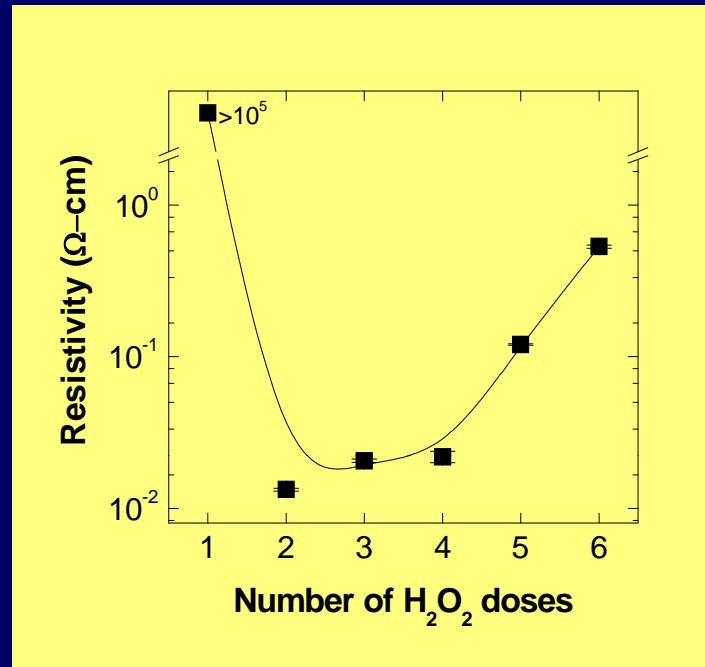


N-type semiconductor by Hall measurements

electron concentration $\sim 10^{20} \text{ cm}^{-3}$

electron mobility $\sim 6 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$


Resistivity vs. Deposition Temperature

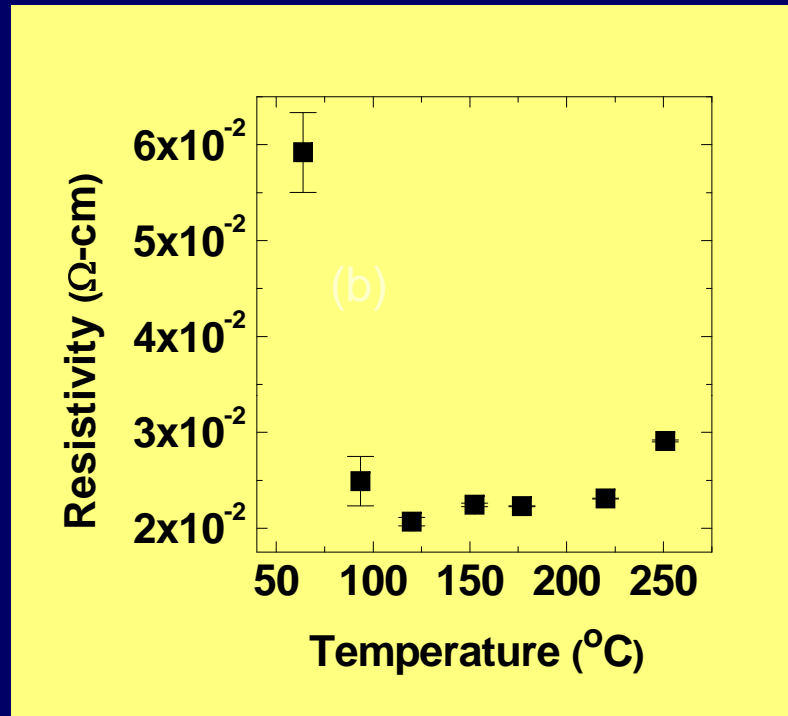


minimum resistivity $0.02 \Omega\text{-cm}$ when deposited at 120°C

Proposed Mechanism

Ligand exchange of Sn precursor with hydroxylated surface

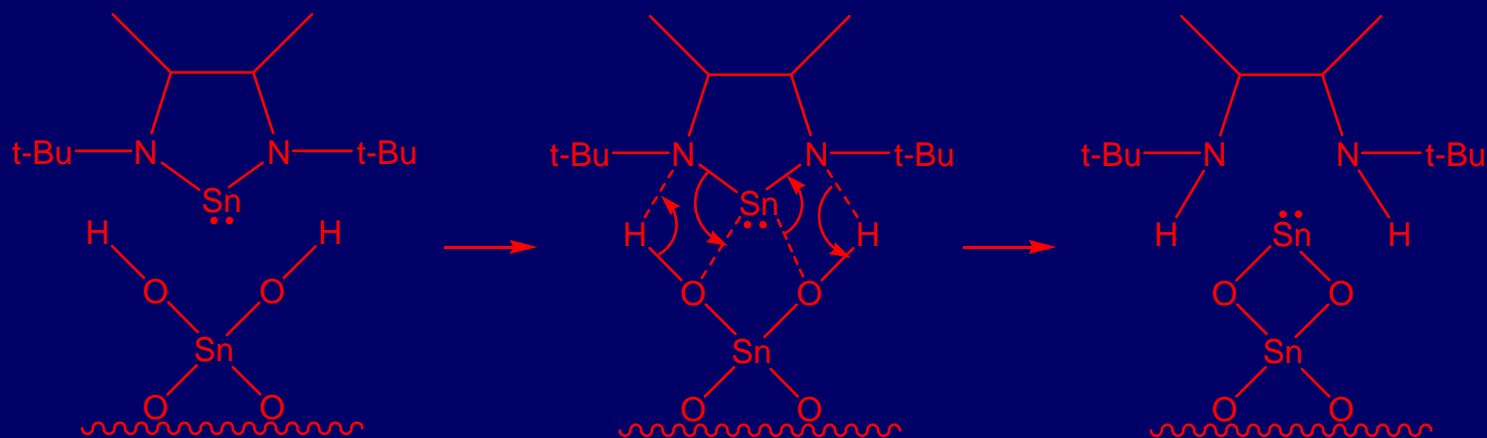

Oxidative addition of hydrogen peroxide

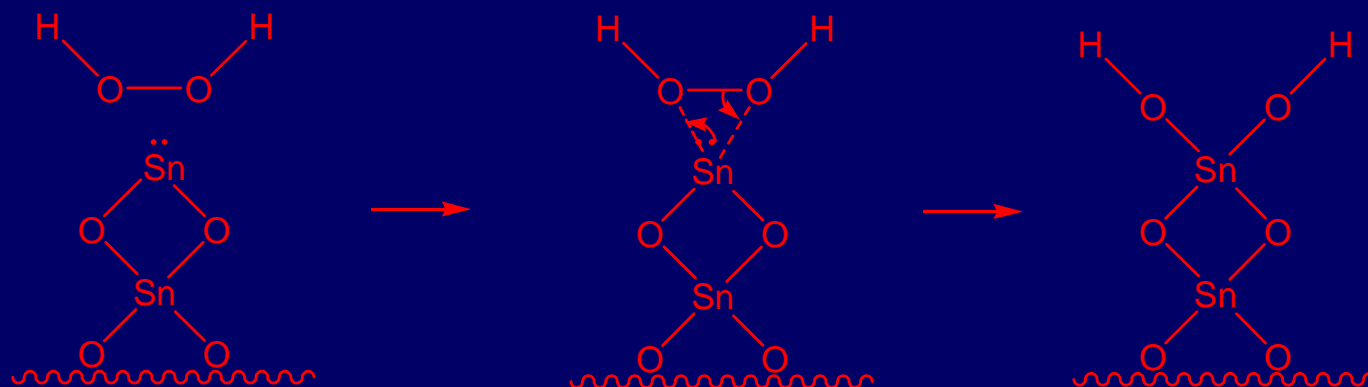

Summary

SnO₂ is transparent semiconductor made of earth-abundant, inexpensive, non-toxic elements

ALD from a cyclic tin(II) amide and H₂O₂ => SnO₂

Smooth films of pure, stoichiometric, polycrystalline SnO₂

High optical transparency and electrical conductivity

Successfully used in several applications:

organic solar cells (with Alan Heeger, UCSB)

conducting and protective coatings for plastics

(with Michelle Schulberg, Physical Sciences Inc.)

**electron multipliers (Philippe deRouffignac, Arradiance,
to be presented on Wednesday at 13:30)**

another possible application: thin-film transistors on plastic

Acknowledgements

Hall measurements done with Mark Winkler and Eric Mazur

Support was provided by the following:

Camille and Henry Dreyfus Postdoctoral Program in Environmental Chemistry

Air Force Office of Scientific Research-STTR under contract FA9550-09-C-0075

Center for Nanoscale Systems (CNS), a member of the National Nanotechnology Infrastructure Network (NNIN), which is supported by the National Science Foundation under NSF award no. ECS-0335765. CNS is a part of the Faculty of Arts and Sciences and the School of Engineering and Applied Sciences at Harvard University.